

This is the accepted version of this paper. It is subject to the conditions of use stated here.  
The version of record is available at <https://doi.org/10.1007/s11696-021-01882-7>

# Use of a Schiff base-modified conducting polymer electrode for electrochemical assay of Cd(II) and Pb(II) ions by square wave voltammetry

Mohammed Q. Mohammed<sup>1\*</sup>, Hani K. Ismail<sup>2</sup>, Hasan F. Alesary<sup>3\*</sup>, Stephen Barton<sup>4</sup>

<sup>1</sup>Department of Chemistry, College of education for pure sciences, University of Basrah, Basrah, Iraq

<sup>2</sup>Department of Chemistry, Faculty of Science and Health, Koya University, Koya KOY45, Kurdistan Region - F.R., Iraq

<sup>3</sup>Department of Chemistry, College of Science, University of Kerbala, Karbala, Iraq

<sup>4</sup>Kingston University London, School of Life Sciences, Pharmacy and Chemistry, Kingston-Upon-Thames, Surrey, UK

\*Corresponding author E-mail: [mahammed.qasim@uobasrah.edu.iq](mailto:mahammed.qasim@uobasrah.edu.iq) ORCID: <https://orcid.org/0000-0003-4998-0647>

[hasan.f@uokerbala.edu.iq](mailto:hasan.f@uokerbala.edu.iq) ORCID: <https://orcid.org/0000-0002-3116-5145>

## Abstract

The work herein describes the electrochemical detection of heavy metal ions, specifically cadmium and lead. The introduction and modification of functional groups such as Schiff bases leads to an enhanced sensitivity of the electrode to analytes. In this study, a platinum electrode has, for the first time, been modified with poly(3,4-ethylenedioxythiophene) (PEDOT/Schiff base) in CH<sub>2</sub>Cl<sub>2</sub> containing Bu<sub>4</sub>NPF<sub>6</sub> to detect cadmium (II) and lead (II) ions. The structures and morphologies of the polymer coatings were characterised via Fourier transform infrared (FTIR) spectroscopy and scanning electron microscopy (SEM), respectively. The electrochemical synthesis and redox state response in monomer-free synthesised films have been studied via cyclic voltammetry. Moreover, the effect of scan rate on the electrochemical behaviour of the modified electrodes was also studied. The voltammetric findings have been used to calculate the surface coverage required for the polymer films and the stability of polymer electrodes in the monomer-free solutions. Square wave voltammetry (SWV) was applied for the determination of cadmium (II) and lead (II) ion concentrations and to assess the effects of pH on aqueous samples. The limits of detection for the modified electrode for cadmium (II) and lead (II) were found to be 0.95 µg L<sup>-1</sup> and 1.84 µg L<sup>-1</sup>, respectively. These findings revealed that modified films can be considered good candidates for application in electrochemical detection devices.

**Key words:** Square wave voltammetry, electrochemical detection, conducting polymers, modified electrode poly(3,4-ethylenedioxythiophene), Schiff base.

## Introduction

Globally, the pollution of the planet is one of most vital problems mankind faces because of the widespread and critical damage such pollution can cause (Intarakamhang et al. 2013; Huang et al. 2016). Heavy metal ions like Cu, Hg, Zn, Pb, Ni, and Cd are considered toxic even in extremely low concentrations (Morante-Zarcero et al. 2015). These metal ions can cause significant harm and damage in human organs such as the kidneys, liver, brain, and the lungs and respiratory system (Lu et al. 2018). Recently, contamination from heavy metals has become a significant problem as a result of the rapid development of industrial activities (Muralikrishna et al. 2017). Contamination of the environment, especially with cadmium (II) and lead (II) ions, poses a real danger to human health because these ions are toxic, non-biodegradable, and accumulate in the body over time (Yao et al. 2019). According to World Health Organisation (WHO), the maximum permitted concentrations of cadmium (II) and lead (II) in drinking water are  $5 \mu\text{g L}^{-1}$  and  $50 \mu\text{g L}^{-1}$ , respectively (Gumpu et al. 2015); thus, it becomes necessary to find fast, sensitive, and selective methods for the detection of cadmium and lead in various sample types. There have been several reports of electrochemical methods used to detect cadmium (II) and lead (II) (Xu et al. 2019) and these methods have many positive features compared with other techniques such as quick analysis times, simplicity, they use inexpensive technology, and have high sensitivities (Li et al. 2019).

The key factor in electrochemical voltammetry methods is the manufacture and usage of electrode surfaces that facilitate an electrical potential between the electrode surface and solution interfaces. Polymerisation and chemical adsorption can enhance the analytical functional performance of an electrode in areas such as the sensitivity and selectivity to analytes. A range of diverse materials, such as functionalised graphene oxide, carbon nanotubes (Salmanipour and Taher 2011), and polymer films have previously been used in voltammetric methods for the detection of metal ions.

Electroactive polymers such as polypyrrole (Yin et al. 2012; Bozzini et al. 2015), polyaniline (Alesary et al. 2018; Pillalamarri et al. 2005; Ismail et al. 2019a), poly(3,4-ethylenedioxythiophene) (PEDOT) (Michalska et al. 2004; Duan et al 2020), and their derivatives have high intrinsic conductivities and have been intensively studied to date (Bobacka 2006; Alesary et al. 2021). These materials play a key role in electrocatalysis, energy storage, and electrochemical sensors because of their unique properties such as stability, flexibility, simple synthetic processes, and low costs (Rahman et al. 2008; Ismail et al. 2019b; Abd Ali et al. 2021). In addition, these species have a good congruence with biomolecules. Therefore, these substances have come to represent effective alternatives to many materials used in, for example, batteries, chemical sensors, corrosion inhibitors, actuators, and in medical engineering. Recently, electroactive polymers have been used in the production of promising chemical sensor devices (Bidan 1992). Chemical modification, and indeed the chosen method of preparation, can often be manipulated to achieve the desired mechanical and electrochemical features of such polymers. Thus, electroactive polymers play a vital role in analytical fields and the fabrication of chemical sensors (Sun et al. 2016). A significant advantage of detection devices based on conjugated polymers is that they have the potential to show sensitive and selective properties and fast responses. In recent years, the fabrication of functionalised polymer electrodes has played a critical role in the production of a novel generation of electroanalysis systems with improved sensitivities and selectivities (Mohammed 2018). Several

electrochemical tools based on polymers have been developed for use as detectors for various chemical pollutants (Barsan et al. 2015).

Modified electrodes in electroanalytical chemistry offer an easy and appropriate technology to allow for the examination of the reactions of various substrates and inorganic, organic, and biological species (Raghu et al. 2012; Han et al. 2020; Wang et al. 2012). Chemically modified polymer electrodes can be prepared and controlled using electrochemical techniques that allow for the generation of thin synthetic polymer films (Lei et al. 2014; Mohammed et al. 2020). In modern electroanalytical devices, analytical performance in areas such as sensitivity, selectivity, and stability are dependent on electrode composition due to the straightforward working mechanism and fast responses achieved (He et al. 2018). Various modes can be used that include square wave voltammetry (SWV), which is considered a perfect candidate for sensitivity and quantification of various species such as alkaloids, phenols, vitamins, pesticides, herbicides and fungicides, benzoquinones, proteins, terpenoids, drugs, and heavy metals (Wang et al. 2012; Shervedani and Akrami 2013). A previous study has reported that a modified polyphenanthroline monohydrate/GC electrode displayed good sensitivity and reproducibility for Cd(II) ion detection via SWV (Oztekin et al. 2011). Moreover, polypyrrole films have been modified by insertion of ligand groups into the polymer film, allowing detection of metallic actions. Deshmukh and co-workers reported that an EDTA-modified py/SWNTs polymer film can be used for the detection of  $Pb^{2+}$  in aqueous solution (Deshmukh et al. 2018). Among the diverse electroactive polymers, poly(3,4-ethylenedioxythiophene) (PEDOT) is of particular interest in the area of chemical sensing due to its high conductivity and good environmental stability compared with other electroactive polymer families. Electropolymerisation of the EDOT monomer can be accomplished through its oxidation in the presence of appropriate counter-ions. Schiff bases have emerged as potential chemical detectors for many of the metal ions of general interest as they can selectively bind to specific cations (Vilas-Boas et al. 1998). The aim of the current research is to enhance the sensitivity and selectivity of modified polymer electrodes to be more efficient with regard to metal ion determination and with improved stability, repeatability and conductivity of the electrodes (Etorki et al. 2007; Guadalupe and Abruna 1985). The goals of this project were: (i) to electropolymerise and modify a PEDOT/Schiff base electrode in non-aqueous medium; (ii) to examine the response of the prepared modified polymer electrode using CV; (iii) to study the effect of scan rate; and (iv) to investigate the interaction of the polymer electrode with heavy metal ions, in particular Cd(II) and Pb(II) ions, using square wave voltammetry (SWV).

## Experimental

### Materials and reagents

2-aminomethyl-3,4-ethylenedioxythiophene (EDOT-MeNH<sub>2</sub>) was prepared using the following procedure (Darmanin and Guittard 2013). Chloromethyl-3,4-ethylenedioxythiophene (EDOT-MeCl), salicylaldehyde (98%), potassium phthalimide and hydrazine hydrate were obtained from Sigma Aldrich and used without further purification. Dichloromethane (DCM) (CH<sub>2</sub>Cl<sub>2</sub>, AR; Tianjin Damao Chemical Reagent Factory) was purified by distillation over calcium hydride before use. Tetrabutylammonium hexafluorophosphate (Bu<sub>4</sub>NPF<sub>6</sub>, 99%; Acros Organics) was dried under vacuum at 60°C for 24 h before use. An acetate buffer solution was prepared by adjusting 0.2 M sodium acetate

(Aldrich) to the desired pH through the addition of 0.2 M glacial acetic acid. All the processes were performed in aqueous media and the preparation of the aqueous solutions was carried out using ultrapure quality water.

## Instrumental

Cyclic voltammetry (CV) and square wave voltammetry (SWV) were performed using a PGSTAT20 potentiostat/galvanostat from ECO-Chemie (Utrecht, The Netherlands). The Pt (1 mm) electrode was polished using 0.3  $\mu\text{m}$  alumina and then washed with pure water. The electrodeposition of the EDOT-Schiff (monomer) base on the Pt electrode was achieved via cyclic voltammetry. SWV measurements were obtained via a potentiostat device which contained three electrodes: an Ag/AgCl reference electrode, a platinum plate (2  $\text{mm}^2$ ) counter electrode, and a PEDOT-Schiff base/Pt working electrode. FTIR spectra were recorded to confirm the chemical composition of the films using a Perkin Elmer FTIR Frontier spectrophotometer (Waltham, USA). Scanning electron microscopy (FEI SIRION SEM) was performed to examine the surface morphology of polymer film deposited on the Pt substrate. Cyclic voltammetry was used for the electrochemical polymerisation of EDOT/Schiff base. The voltage range was swept 10 times between  $-0.5$  to  $1.4$  V at various scan rates (10, 20, 30, 50, and  $100$   $\text{mV s}^{-1}$ ). The formation of the polymer layer on the surface of the electrode was evidenced by the emergence of a dark colouration on the working electrode. The polymer film coating was washed using deionised water to eliminate the excess monomer from electrode surface, which was then dried at room temperature.

## Preparation of stock solutions

Standard solutions (100 ppm) of each metal ion were synthesised by dissolving the metal ion in ultrapure deionised water. The lead standard solution was prepared by dissolving 0.1598 g of  $\text{Pb}(\text{NO}_3)_2$  (99.9%, Aldrich) in deionised water and diluting to 1 litre. The cadmium solution was produced by dissolving 0.274 g of  $\text{Cd}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O}$  (99.9%, Aldrich) in ultrapure deionised water and diluting to 1 litre. These stock solutions were used to prepare a series of different concentrations from 5 to 100 ppm for each of the metal ions.

## Preparation of (2,3-dihydrothieno[3,4-b][1,4]dioxin-2-yl)methanamine PEDOT/ $\text{NH}_2$


The original monomer of EDOT- $\text{NH}_2$  was synthesised as illustrated in Scheme 1 according to the procedure described in the literature (Darmanin and Guittard 2013). The substitution of the chloride group by an amine group was achieved via a Gabriel reaction in the presence of potassium phthalimide and hydrazine. A mixture of 2-(chloromethyl)-2,3-dihydrothieno[3,4-b][1,4]dioxine (0.3 g, 1.6 mmol) and potassium phthalimide (0.4 g, 2.2 mmol) were dissolved in 10 ml of dimethylformamide and heated at  $100^\circ\text{C}$  for 24 h. The product was then decanted into 100 ml of water and extracted with chloroform. 0.1 M sodium hydroxide and water were used to wash the organic layer and then dried with  $\text{MgSO}_4$ . After this step, the product was mixed with hydrazine hydrate (0.16 g, 3.2 mmol) and the mixture added to 10 ml of methanol and heated to  $50^\circ\text{C}$  for 1 h. After the reaction had stopped, water was added to the mixture and the solvent was extracted under vacuum. This mixture was acidified with HCl and heated to  $60^\circ\text{C}$  for 1 h. Next, the neutralisation step was accomplished for this solution using 2 M sodium hydroxide. After solvent evaporation, the amine compound was purified via column chromatography (silica gel; eluent: methanol/dichloromethane in a 1:4 ratio).

## Preparation of PEDOT/Schiff ligand

2-aminomethyl-3,4-ethylenedioxythiophene (EDOT–MeNH<sub>2</sub>) (0.55 g, 2 mmol) and salicylaldehyde (0.24 g, 2 mmol) were dissolved in 20 ml of methanol with 2-3 drops of acetic acid as a catalyst under continuous stirring and then refluxed for 5 h according to the procedure described in the literature (Almashal et al. 2020). The reaction was monitored via thin-layer chromatography. At the end of the reaction, the solution obtained was filtered and washed with methanol. The crude product was dried and purified via crystallisation from ethanol. The synthesis of the monomer and polymerisation reaction steps are illustrated in Scheme 1.

## Electropolymerisation of EDOT/Schiff base

The EDOT derivative was synthesised using a condensation reaction with the aldehyde EDOT-Schiff base and electropolymerised in a suitable solution to create the conducting polymer. For voltammetric deposition experiments, the EDOT/Schiff base was electropolymerised on the Pt electrode from a solution of 10 mM EDOT/Schiff base with 0.1 M tetrabutylammonium hexafluorophosphate (Bu<sub>4</sub>NPF<sub>6</sub>) in DCM using voltage cycling between –0.5 V and 1.4 V vs. the reference electrode (Ag/AgCl). The PEDOT/Schiff base film was grown on the Pt surface for 10 sequential scans with increasing anodic and cathodic peak current densities. The modified polymer electrode will hereafter be referred to as the PEDOT/Schiff base.

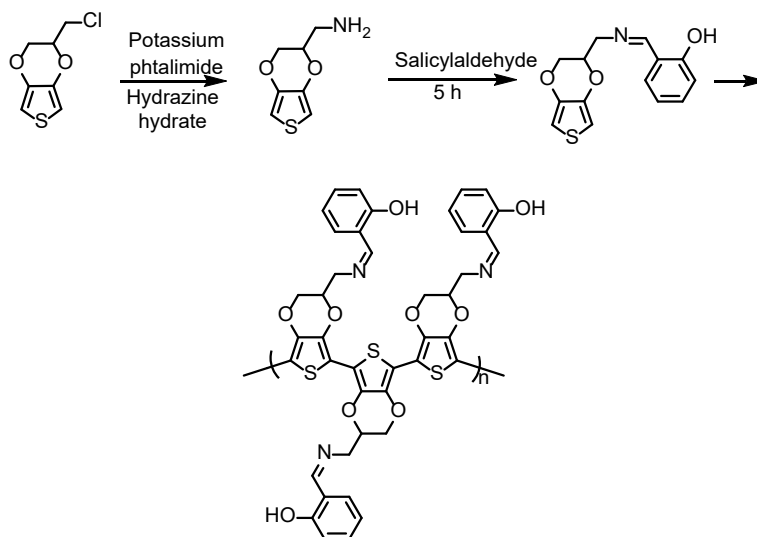

**Scheme 1** The synthesis of the monomer EDOT/ Schiff base and the polymerisation reaction

## Electrochemical detection of metal ions


Electrochemical measurements were performed with an AUTOLAB Analyser using a cell with three electrodes as described above. The working electrode was a PEDOT/Schiff base electrode, the reference electrode an Ag/AgCl/ 3 M KCl electrode, and the auxiliary electrode was a platinum electrode. Acetic acid/sodium acetate (0.2 M CH<sub>3</sub>COOH + 0.2 M CH<sub>3</sub>COONa) buffer solutions (pH 2-6) containing different concentrations of cadmium (II) and lead (II) ions were used as the electrolytes for all measurements. All experiments were conducted at ambient temperature, 25 ± 2°C.

Square wave voltammetric parameters were as follows: initial potential -0.5 V, end potential 1.5 V, pulse amplitude 10 mV.

## Results and discussion

### Electrochemical formation of PEDOT/Schiff

The poly(EDOT-Schiff base) film was prepared potentiodynamically with a voltage ranging between -0.50 V and 1.40 V over ten scans from a 0.1 M solution of monomer in CH<sub>2</sub>Cl<sub>2</sub> containing Bu<sub>4</sub>NPF<sub>6</sub> onto a Pt electrode at a scan rate of 10 mV s<sup>-1</sup> at 25 ± 2°C. **Fig. 1** illustrates the cyclic voltammograms that were recorded during the synthesis of poly(EDOT-Schiff base). As shown in **Fig. 1**, the onset of the oxidation potential for the PEDOT-Schiff base film was 1.22 V. During polymerisation, a black-coloured layer of polymer film formed on the Pt electrode. The current peak of the polymer film increased with increasing number of cycles, which corresponds to the systematic growth of a polymer film on the Pt electrode (Schultheiss et al. 2020). The cyclic voltammogram in **Fig. 1** shows a nucleation loop in the first cycle where this anodic current related to the oxidation of the monomer and nucleation of poly(EDOT/Schiff) (Ismail et al. 2019a). The nucleation loop was not present in the following cycles because of the persistent growth of the film preventing further nucleation in the subsequent scans. The redox processes of poly(EDOT/Schiff) has led to the emergence of anodic and cathodic peaks at 0.53V and -0.07 V, respectively, in the cyclic voltammogram. Moreover, the increase in redox peak current values in the voltammogram implied that the amount of electrodeposited PEDOT polymer on the Pt electrode had increased, which led to an increased thickness of the deposited polymer (Hillman et al. 2017). In addition, two peaks probably indicate the potential peaks of the monomers, which depended on the type and of size the anion present in the reaction medium. In other words, the emergence of redox peaks in the voltammogram can be significantly influenced by the nature and size of the ionic species present in the electrolyte.

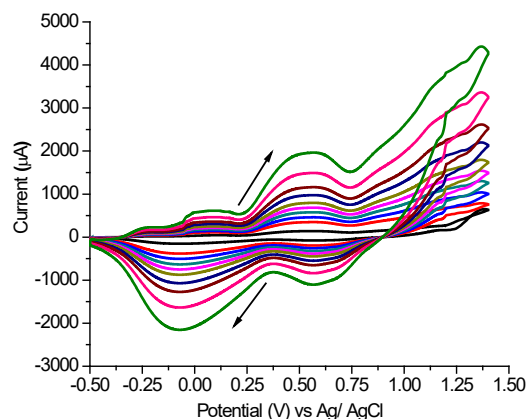

**Fig. 1** Cyclic voltammogram resulting from electropolymerisation of 10 mM EDOT/Schiff base with 0.1 M Bu<sub>4</sub>NPF<sub>6</sub> in DCM solution between -0.5 and 1.4 V at 10 mV s<sup>-1</sup> for 10 scans. Electrode area was 0.00785 cm<sup>2</sup>.

**Fig. 2** shows the cyclic voltammogram (scan 10) of the electropolymerisation of the (EDOT/ Schiff) monomer at various scan rates ranging from 5 - 100 mV s<sup>-1</sup> under the same polymerisation conditions used for the voltammogram

in **Figure 1**. The molar coverage of polymer films per unit area can be calculated from the amount of charge of the final scan in the polymer deposition using Faraday's law and **Eq. 1** (Sapstead et al. 2015).


$$\Gamma = \frac{Q}{nFA} \quad (1)$$

Here,  $F$  represents the Faraday constant ( $C \text{ mol}^{-1}$ ),  $\Gamma$  is the molar coverage ( $\text{mol cm}^{-2}$ ),  $A$  is the modified electrode area ( $\text{cm}^2$ ),  $Q$  represents the cathodic charge, and  $n$  is the number of electrons involved in the electropolymerisation. Herein,  $n$  is equal to 2.3 (Lattach et al. 2012) and the modified electrode has a surface area of  $0.00785 \text{ cm}^2$ . The molar coverage is applied to estimate the thickness of the polymer surface ( $h/\mu\text{m}$ ) using **Eqs. 2 and 3** (Brown and Hillman 2012).

$$c = \frac{\rho}{Mr} \quad (2)$$

$$h = \frac{\Gamma}{c} \quad (3)$$

Here,  $c$  and  $\rho$  are the concentration and density of the monomer, respectively, and  $Mr$  is the molecular mass of the monomer ( $273.3 \text{ g/mol}$ ).  $h$  is the thickness of polymer film. The relative standard deviation (RSD%) from three consecutive experiments was calculated, as shown in **Table 1**, which also reports the cathodic charge, surface coverage, and thickness of prepared polymer films.

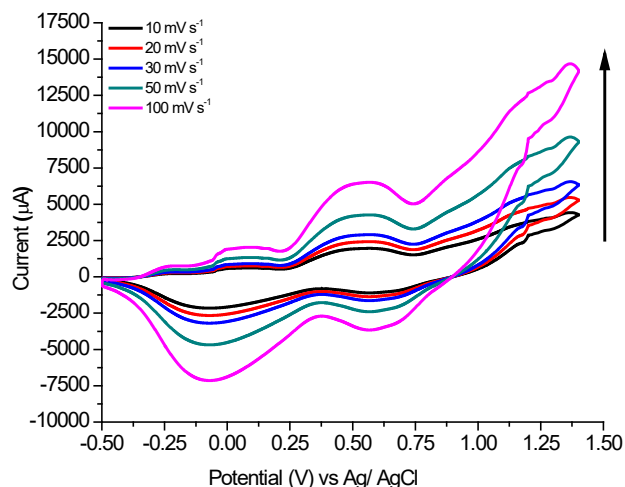

**Fig. 2** Cyclic voltammogram (scan 10) for deposition of 10 mM EDOT/Schiff base with 0.1 M  $\text{Bu}_4\text{NPF}_6$  in DCM solution at various scan rates,  $v$ , 5-100  $\text{mV s}^{-1}$ . Electrode area is  $0.00785 \text{ cm}^2$ .

**Table 1** Charge of poly(EDOT/Schiff) reduction peak at various scan rates (5-100  $\text{mV s}^{-1}$ ). Electrode area was  $0.00785 \text{ cm}^2$ .




Polymer films	Scan rate (mV s <sup>-1</sup> )	Charge of reduction peak <i>Q</i> (C)	RSD% n=3	Coverage <i>Γ</i> (mol cm <sup>-2</sup> )	Thickness <i>h</i> (μm)
poly(EDOT/Schiff)	10	1.30 × 10 <sup>-2</sup>	1.32	7.46 × 10 <sup>-6</sup>	14
	20	1.12 × 10 <sup>-2</sup>	2.45	6.42 × 10 <sup>-6</sup>	12
	30	9.15 × 10 <sup>-3</sup>	1.85	5.25 × 10 <sup>-6</sup>	10.5
	50	8.02 × 10 <sup>-3</sup>	2.06	4.60 × 10 <sup>-6</sup>	9.22
	100	6.11 × 10 <sup>-3</sup>	1.47	3.50 × 10 <sup>-6</sup>	7.01

### Electrochemical characterisation of polymer films

In order to obtain a greater insight into the electrochemical behaviour and stability of the polymer films, the electrochemical features were carefully analysed via cyclic voltammetry in a background electrolyte (monomer-free) of dichloromethane and aqueous solution-Bu<sub>4</sub>NPF<sub>6</sub> (0.1 M) for polymer film that was prepared using a scan rate of 10 mV s<sup>-1</sup> (Fig. 1), as depicted in Fig. 3A and 3C. Voltammetric study findings have shown broad redox current peaks that can probably be attributed to the counterions diffusing into the chain polymer film for both electrolytes (Mohammed 2018). The voltammograms of poly(EDOT/Schiff) films exhibit a broad positive peak at 0.61 V vs. Ag/AgCl and a negative peak at 0.08 V vs. Ag/AgCl in a DCM electrolyte. On the other hand, a broad positive peak appears at 0.52 V vs. Ag/AgCl and a negative peak at 0.16 V vs. Ag/AgCl in aqueous electrolyte, which are representative of the oxidation and reduction of the film produced, respectively. Herein, we observed a decrease in the peak currents as a function of increasing scan number; thus, there is decay in the peak potentials and the associated CV shapes were changed. This could be attributed to degradation of the film when switching to the overoxidation potential, which led to poor stability during redox cycling. In order to study the degradation of poly(EDOT/Schiff) and it can be proposed in any practical application of their sensor system, the long-term of electrochemical stability of the prepared poly(EDOT/Schiff) electrode (Fig. 1) was studied in aqueous electrolyte (monomer-free) for 200 scans. The results showed that poly(EDOT/Schiff) has a high electrochemical stability; thus, there is no shift in the peak potentials and the associated CV shapes were not changed (See supplementary information Fig. S1).


In this work, the effect of scan rate on electrochemical response has been studied in a background electrolyte (monomer-free) of dichloromethane and aqueous solution-Bu<sub>4</sub>NPF<sub>6</sub> (0.1 M), as shown in Fig. 3B and Fig. 3D. From these two curves, we can observe that the current of the peak was proportional to the scan rate (Ouyang et al. 2017); this supports the assumption of good electro-activity and stability of the polymer film. This finding indicates that redox current peaks are proportional to the scan rates for the same polymer electrode (Deshmukh et al. 2018). Further, both oxidation and reduction peaks have a linear relationship with scan rate, which is indicative of surface-confined control, as revealed in Figs. 4A and 4B. Tables 2 and 3 show the charges for the electrochemical response of polymer growth in Fig. 1 as cycled in the background electrolyte (monomer-free) at different scan rates, as presented in Fig. 3B and 3D. The charge was calculated from the CV curves in Fig. 3B and 3D by integration of the current of the redox peaks with respect to time. The charges found for cycles 1 and 10 are shown in Tables 2 and 3. Tables 2 and 3

show the cathodic charge values and a study of the electro-stability of the prepared films (at various scan rates in the range 10 – 100  $\text{mV s}^{-1}$ ). The electro-stability was calculated via cyclic voltammetry from the difference between the tenth and first cycles in two monomer-free electrolytes. The results show that increasing the scan rate for PEDOT/Schiff growth results in a decrease in the charge (i.e., 1<sup>st</sup> and 10<sup>th</sup> cycles) for the polymer film exposed to 0.1 M  $\text{Bu}_4\text{NPF}_6$  in DCM and aqueous electrolytes (monomer-free).

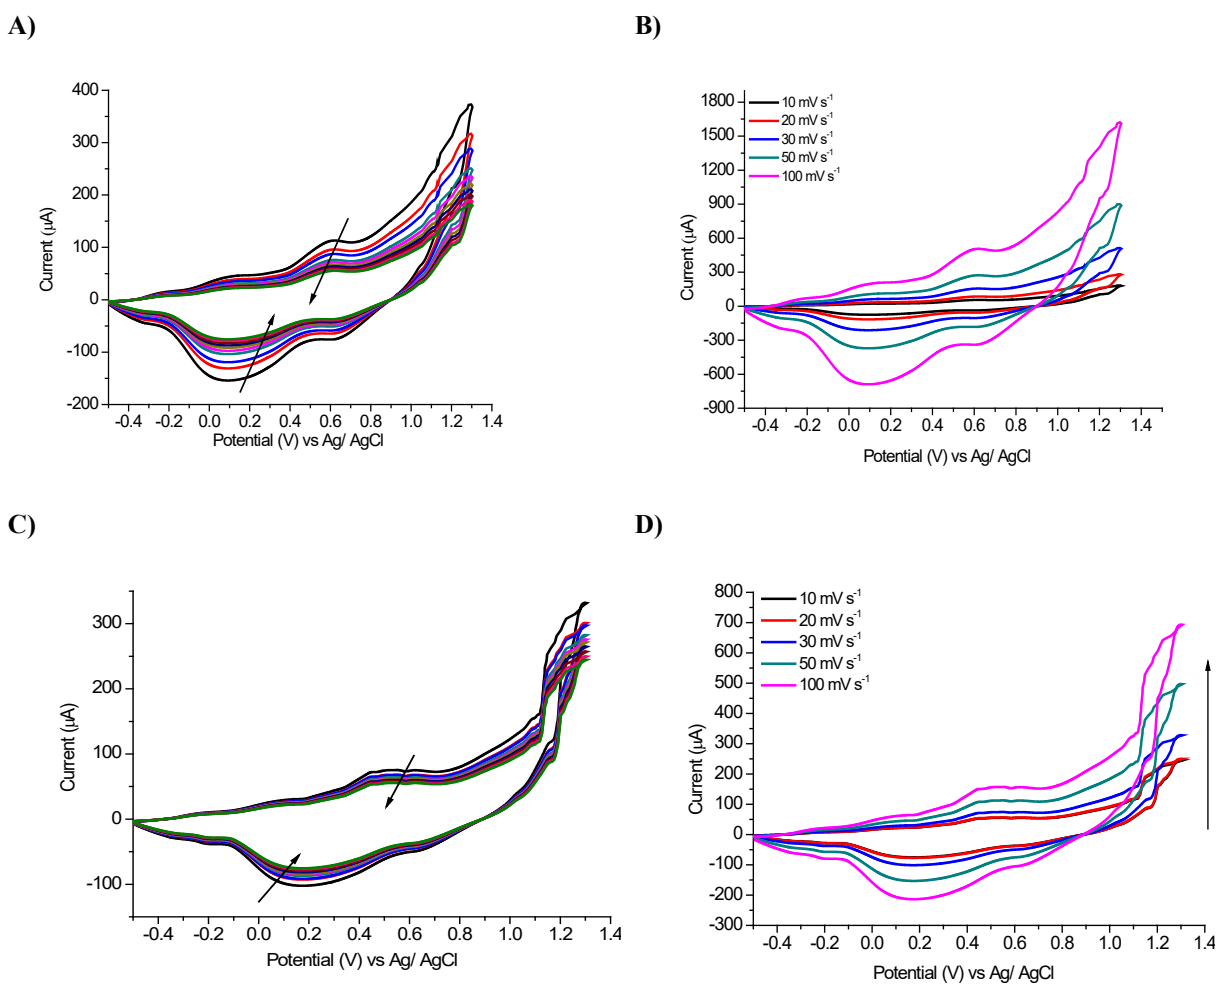


**Fig. 3** Voltammetric response of poly(EDOT/Schiff) electrodes prepared at 10  $\text{mV s}^{-1}$  (**Figure 1**) and acquired in **A**) 0.1 M  $\text{Bu}_4\text{NPF}_6$  in DCM, and **C**) 0.1 M  $\text{Bu}_4\text{NPF}_6$  in the aqueous electrolyte (monomer-free) at -0.5 to 1.3 V. Voltammetric responses of the same polymer film at various scan rates in the range 10-100  $\text{mV s}^{-1}$  **B**) DCM and **D**) aqueous electrolyte.

A)

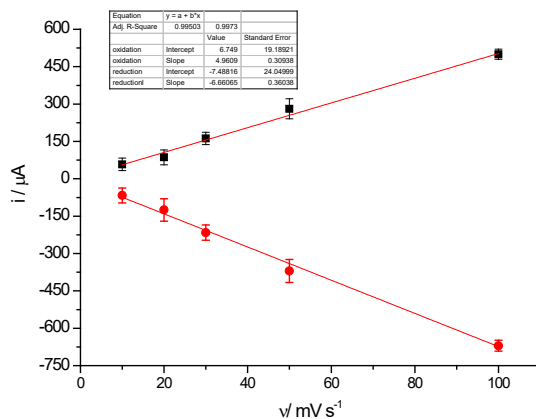

B)

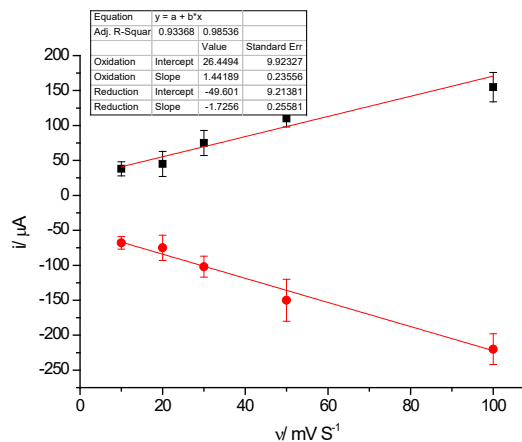

**Fig. 4** Variation of redox peak current **A)** from **Figs. 3B** and **B)** from **Fig. 3D** with scan rate (in the range 10-100  $\text{mV s}^{-1}$ ).

**Table.2** Cathodic charges of PEDOT/Schiff panels in **Figure 1** exposed to 0.1 M  $\text{Bu}_4\text{NPF}_6$  in DCM electrolyte (monomer-free) at various scan rates.


Scan rate $\text{mV s}^{-1}$	$Q_{\text{red, 1st cycle C}}$	$Q_{\text{red, 10th cycle C}}$	% $Q_{\text{red 10th}} / Q_{\text{red 1st}}$ retention
10	$8.45 \times 10^{-3}$	$6.12 \times 10^{-3}$	72
20	$5.89 \times 10^{-3}$	$4.78 \times 10^{-3}$	81
30	$4.78 \times 10^{-3}$	$3.96 \times 10^{-3}$	82
50	$4.08 \times 10^{-3}$	$3.08 \times 10^{-3}$	75
100	$2.64 \times 10^{-3}$	$2.25 \times 10^{-3}$	85

**Table.3** Cathodic charges of PEDOT/Schiff panels in **Figure 1** exposed to 0.1 M  $\text{Bu}_4\text{NPF}_6$  in aqueous electrolyte (monomer-free) at various scan rates.

Scan rate	$Q_{\text{red, 1st cycle C}}$	$Q_{\text{red, 10th cycle C}}$	% $Q_{\text{red 10th}} / Q_{\text{red 1st}}$ retention
10	$8.19 \times 10^{-3}$	$6.12 \times 10^{-3}$	77
20	$3.71 \times 10^{-3}$	$3.08 \times 10^{-3}$	83
30	$2.97 \times 10^{-3}$	$2.68 \times 10^{-3}$	90
50	$2.13 \times 10^{-3}$	$2.45 \times 10^{-3}$	87
100	$1.86 \times 10^{-3}$	$1.70 \times 10^{-3}$	91

FTIR characterisation of EDOT/ $\text{NH}_2$  and PEDOT/Schiff base structures

**Fig. 5** illustrates the FTIR spectra of EDOT/ $\text{NH}_2$  and electrochemically prepared poly(EDOT/Schiff base) structures. An FTIR spectrum of PEDOT/ $\text{NH}_2$  has the distinctive features of PEDOT and the amino group. The bands of the  $\text{NH}_2$  group vibrations were observed in the range  $3380 - 3240 \text{ cm}^{-1}$ . The peaks at  $3090 \text{ cm}^{-1}$  and  $2975 \text{ cm}^{-1}$  were assigned to C–H aromatic and C–H aliphatic stretches, respectively. The vibrations for the C–O–C and C–S groups in EDOT were observed at  $1100 \text{ cm}^{-1}$ ,  $940 \text{ cm}^{-1}$ , and  $615 \text{ cm}^{-1}$ , respectively. The bands at  $1641$ ,  $1535$  and  $1362 \text{ cm}^{-1}$  were attributed to the C=C and C–C stretches in the thiophene cycle (Ouyang et al. 2017). The FTIR spectrum of the prepared polymer Schiff base had characteristics peaks at  $1645 \text{ cm}^{-1}$  and  $3365 \text{ cm}^{-1}$  that could be attributed to imine (C=N) and OH groups, respectively. The band at  $2939 \text{ cm}^{-1}$  was assigned to the C–H aromatic and dioxyethylene bridge stretching modes of the EDOT molecule. Further, the bands at  $1128 \text{ cm}^{-1}$  and  $975 \text{ cm}^{-1}$  were noted for EDOT/Schiff (Deshmukh et al. 2018).

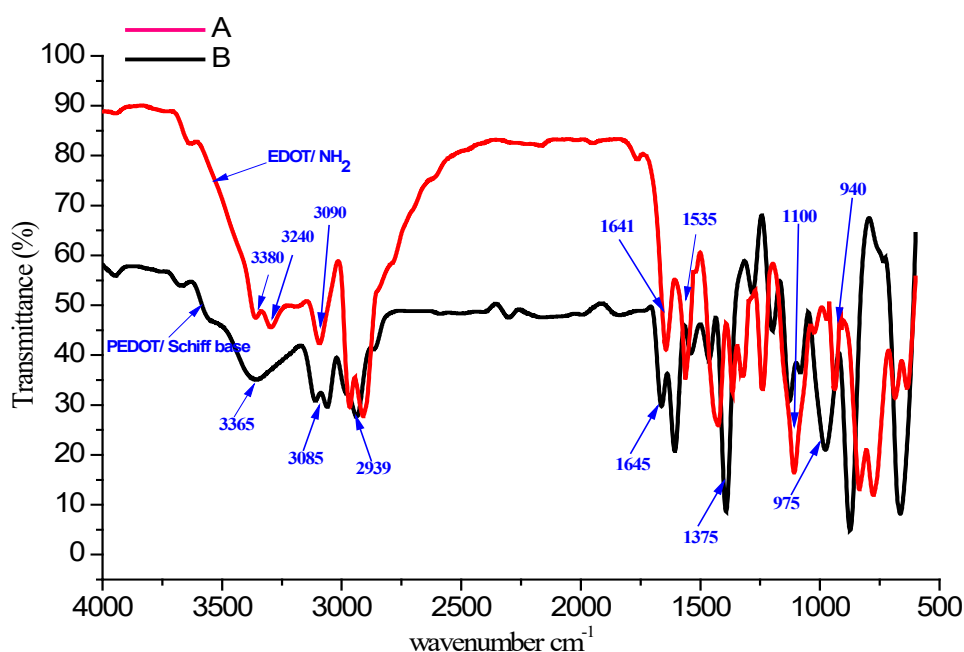


**Fig. 5** FTIR spectra of A) synthesised monomer (red line) and B) synthesised poly(EDOT/Schiff base) (black line).

### Morphological characterisation of PEDOT/Schiff base

The surface morphology of the PEDOT-Schiff film electrodeposited on the Pt electrode before and after adsorption of metal ions (Cd(II) and Pb(II)) was analysed by scanning electron microscopy (SEM) to characterise the morphology and surface structure of the film (Figure 6). The polymer film was prepared potentiodynamically by applying a potential in the range  $-0.5$  to  $1.5 \text{ V}$  vs. Ag/AgCl at a scan rate of  $10 \text{ mV s}^{-1}$  for 10 cycles. Fig. 6(A) shows that the PEDOT-Schiff film has uniform particles with a globular morphology before adsorption. Further, the SEM image (Fig. (A)) clearly exhibits particles of different grain sizes in the nanometre range, confirming the nanostructure of the prepared polymer composite. However, the morphological surface of the polymer composite changed after adsorption (Fig. 6(B)), indicating the presence of lead and cadmium ions on the surface electrode of the polymer composite. The

variation in morphology of the polymer occurs due to the dissolution of ions from the prepared polymer composite and deposition of lead and cadmium metal ions on the surface of the polymer composite. Therefore, these variations in the surface morphology can be attributed to the interaction of the PEDOT-Schiff composite with Cd(II) and Pb(II) solutions through coordinative bonding and electrostatic interactions between the Cd(II) and Pb(II) ions and the polymer (as sorbent). In general, the morphology of the polymer surface is significantly affected by the experimental conditions, such as the pH, temperature, solvent type, ions present, and scan rates used (Niu et al. 2001). Energy-dispersive X-ray (EDX) spectra, as shown in Fig. 12, confirmed the presence of Pb(II) and Cd(II) ions on the composite surface following exposure to these ions in solution.

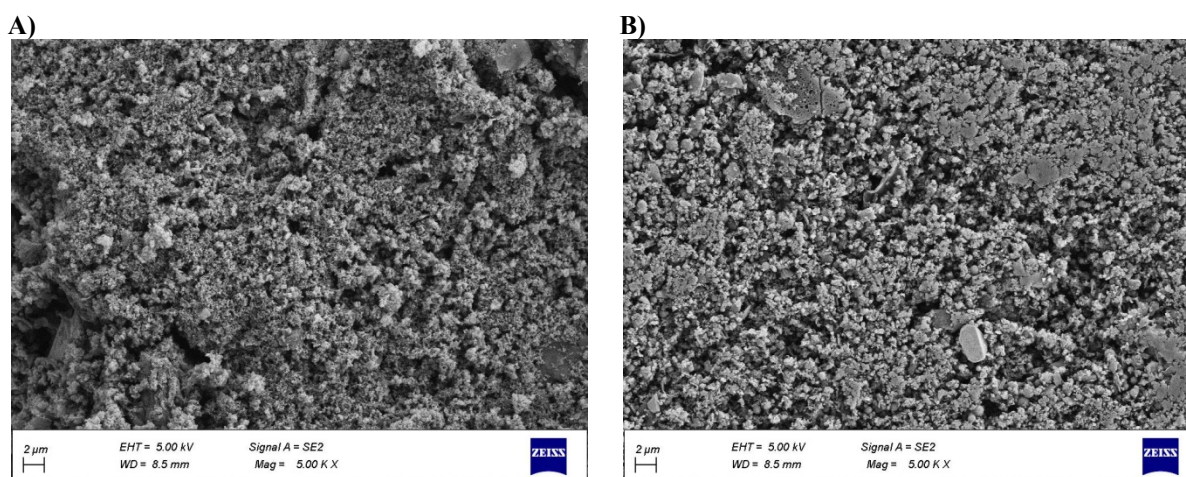


**Fig. 6** SEM images of (A) poly(EDOT/Schiff) formed using electropolymerisation at a scan rate  $10 \text{ mV s}^{-1}$  before adsorption, and (B) poly(EDOT/Schiff) after adsorption of metal ions (see the conditions in Fig. 11).

## Influence of pH

It is unquestionable that pH directly influences the shapes of the voltammograms, and it is thus important to consider the effect of pH on electrochemical processes (Hassan et al. 2018). The pH of the solution notably affects the type of metal ions and the functional groups on the electrode surface. For example, in an acidic electrolyte, the functional groups at the polymer surface will be converted to the protonated form, while in the basic electrolyte metal ions may form hydroxides and precipitate out of solution. Therefore, the chemical bonding of imine groups with metal ions will be significantly affected by the pH of the electrolyte. Low pH will deactivate the imine group, whereas high pH will lead to the formation of metal hydroxides and inhibit the accumulation of metals. According to Panday et al, it is important to achieve the highest peak current possible during experimentation (Pandey et al. 2019).

Analyte solutions containing  $5 \mu\text{g L}^{-1}$  of Cd(II) and Pb(II) ions in media with different pHs were used for the voltammetric investigation. The square wave voltammograms exhibited clear peaks for metal ions in media with diverse pH values. It was found that the peak current shapes and heights in a solution of pH 5 were well-defined and higher compared to those recorded at other pHs. Thus, pH 5 was considered the most suitable for the determination of ion concentrations in solution. The findings obtained are graphically depicted in **Fig. 7** where, as shown, the modified electrodes have low current peaks in highly acidic solution (pH 2), after which the current peak increases


with increasing pH until reaching pH 5, which was subsequently used for the analysis of cadmium and lead cation concentrations.

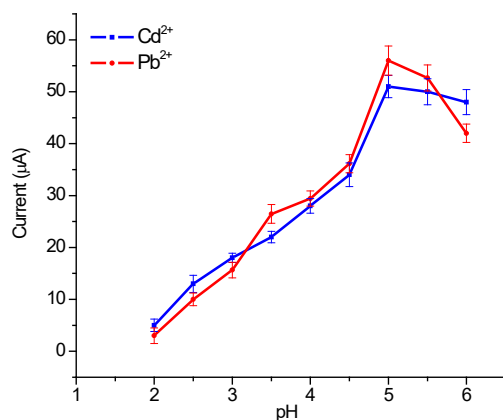

**Fig. 7** Plot of SWV peak currents for Cd and Pb ions as a function of pH as obtained on PEDOT/Schiff electrodes.

### Measurement of Cd(II) and Pb(II) using SWV

The procedure for the electro-analytical determination of cadmium and lead concentrations in aqueous solution was divided into two steps. Firstly, the modified electrode was immersed in a sample solution containing the analyte (Cd(II) or Pb(II)) at a known pH of 5 and a selected concentration ( $5 - 100 \mu\text{g L}^{-1}$ ), where metal ions were binding chemically to the ligands at the surface of the electrode; and, secondly, the polymer electrode was removed from the metal ion solution and rinsed with deionised water and then transferred to a voltammetric cell containing only a supporting electrolyte (acetate buffer solution). The square wave voltammograms were performed using various cadmium and lead concentrations. **Fig. 8** shows the proposed interaction between the polymer ligand and metal ions.

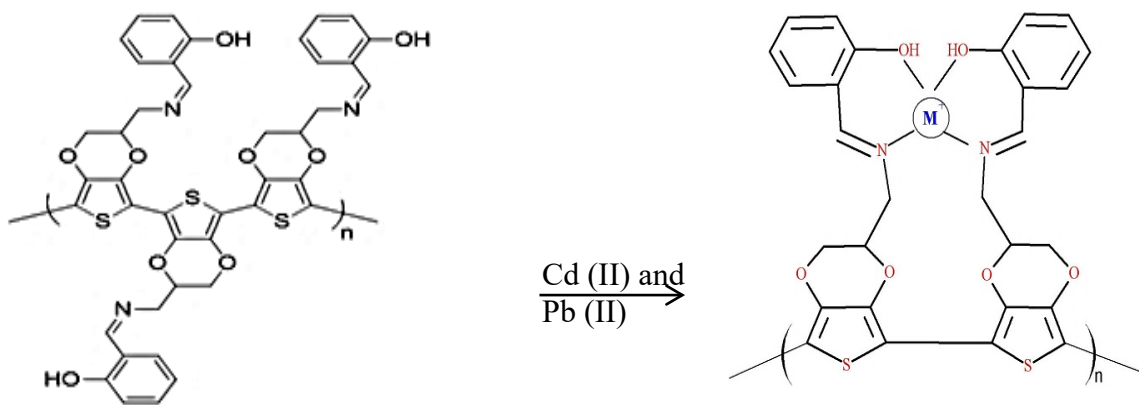


**Fig. 8** Assumed schematic for the formation of the PEDOT/Schiff-metal ion complexes.

### The determination of Cd(II) and Pb(II) ions

Optimal practical conditions for the determination of Cd(II) and Pb(II) ions by the PEDOT/Schiff electrode using the SWV technique were separately assessed for each electrode. Initially, the current responses were recorded for the polymer electrodes using a blank solution without metal ions. The blank solution responses did not have any current signals in the voltage range from  $-1.2$  to  $0$  V, as illustrated in **Fig. 9** (black line). Accumulation of the Cd(II) and Pb(II) ions occurred by immersion of the modified electrode in buffer solution at pH 5 containing Cd(II) and Pb(II) ions. This process led to complex formation between the metal ions and the PEDOT/Schiff base layer. The chemical accumulation process which occurred for Cd(II) and Pb(II) ions probably affected the accumulation of other reducible species at the voltage used during the preconcentration processes. After the immersion of metal ions in the PEDOT/Schiff electrode, they were washed with pure water. After that, the modified electrode was moved to the electrochemical cell, which contained buffer solution. The SWV response was registered for each metal ion, i.e., Cd(II) and Pb(II) (Fourou et al. 2016; Zhang et al. 2020).


The square wave voltammograms of modified electrodes, after 15 min of immersion in buffer solution, at pH 5 with  $5 \mu\text{g L}^{-1}$  of Cd(II) and Pb(II) ions, are shown in **Fig. 9**. The determination of Cd(II) and Pb(II) ion concentrations was investigated between  $-1.2$  to  $0.0$  V (vs. Ag/AgCl). As can be noted in **Fig. 9**, the interaction of the Cd(II) and Pb(II) ions with the modified electrode surface leads to the alteration of the electrochemical properties of the electrode. Clearly, the anodic peak has increased due to Cd(II) and Pb(II) ions, which formed a complex on the modified electrode (**Fig. 9**) compared with the peak current recorded after immersion of the same electrode in solution without metal ions (**Fig. 9, A and B**).

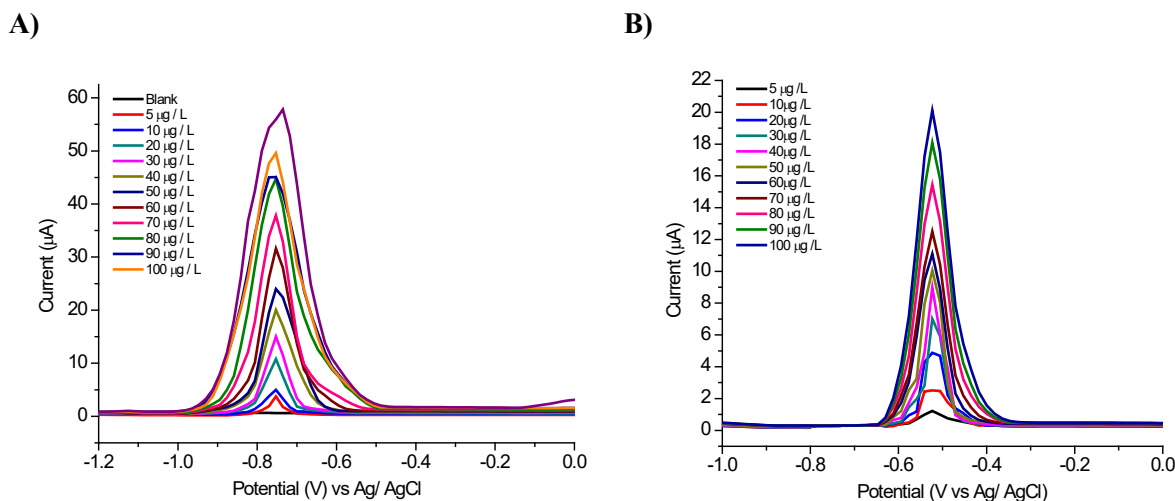

**Fig. 9** SWV curves for different concentrations of (A) Cd(II) and (B) Pb(II) from lower to higher concentration ( $5$ - $100 \mu\text{g L}^{-1}$ ) using a poly(EDOT/Schiff) electrode.

The calibration equations and correlation coefficients ( $R^2$ ) were calculated for the Cd(II) and Pb(II) ions as  $y = 1.639 + 0.434x$  ( $x: \mu\text{g L}^{-1}$ ,  $y: \mu\text{A}$ ),  $R^2 = 0.9989$  for Cd(II) and  $y = 0.492 + 0.159x$ ,  $R^2 = 0.9961$  for Pb(II), respectively, as shown in **Fig. 10**. The limits of detection (LOD) were determined to be  $0.95 \mu\text{g L}^{-1}$  and  $1.84 \mu\text{g L}^{-1}$  for the Cd(II) and

Pb(II) ions, respectively, which demonstrates the high sensitivity of the modified polymer electrode towards heavy metal ion detection. The separation in peaks locations for metal ions offer an accurate strategy to detect Cd(II) and Pb(II) ions, significantly reducing interfering effects from other heavy metal ions (Dang et al. 2018; Zhai et al. 2018). Calibration was performed to allow for the determination of metal ions at pH 5 in buffer solution. **Fig. 10** shows square wave voltammograms recorded using consecutive additions of ion metals over the 5 - 100  $\mu\text{g L}^{-1}$  concentration range at the EDOT/Schiff modified electrode. Peak currents appeared at -0.77 V and -0.50 V for the various concentrations of Cd(II) and Pb(II), respectively (**Fig. 9**). A linear relationship between the concentration of ion metals and current peaks was evident from the experimental findings.

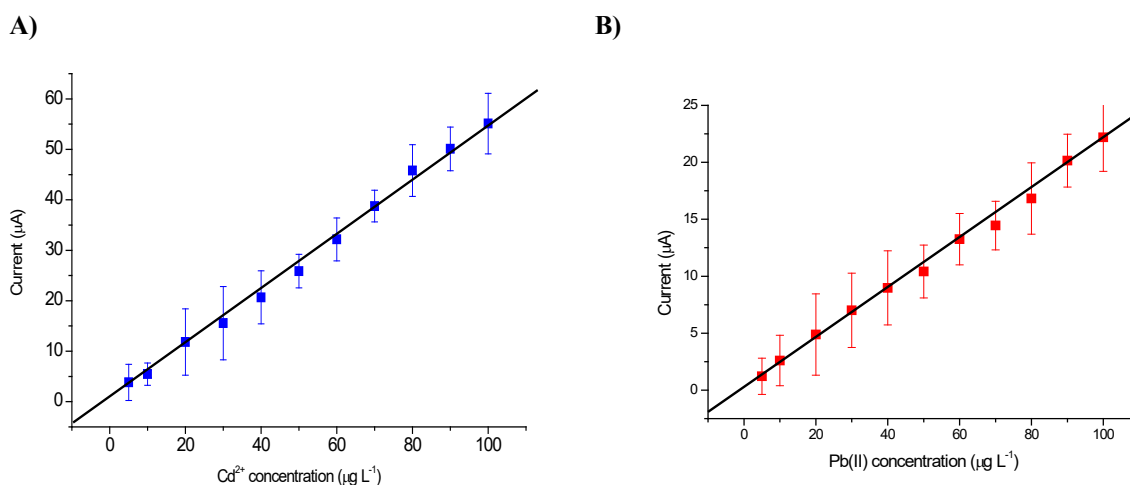


**Fig. 10** Calibration plot for measurement of different concentrations (5 - 100  $\mu\text{g L}^{-1}$ ) of (A) Cd(II) and (B) Pb(II) taken from **Fig. 9** using a poly(EDOT/ Schiff) electrode.

### Simultaneous electrochemical determination of Cd(II) and Pb(II) in a binary mixture

The analytical signal of various concentrations of Cd(II) and Pb(II) ions is illustrated in **Figs. 9A** and **9B**, respectively. Subsequently, the simultaneous determination of Cd(II) and Pb(II) ions with the PEDOT/Schiff electrode was carried out to detect Cd(II) and Pb(II) ions in the same solution (Hassan et al. 2019). SWV voltammograms of the PEDOT/Schiff electrode after sequential additions from different concentrations of Cd(II) and Pb(II) are shown in **Fig. 11**. The characteristic peaks of Cd(II) and Pb(II) were seen at -0.77 and -0.50 V, respectively. These findings were in agreement with the individual species' characteristics (**Fig. 9**). The effects of ion concentrations were examined under optimum conditions. Metal ion concentrations were examined between -1.2 to 0.0 V (vs. Ag/AgCl) at various concentrations in the range 5  $\mu\text{g L}^{-1}$  to 100  $\mu\text{g L}^{-1}$  for Cd(II) and Pb(II), respectively. **Fig. 11** represents the square voltammograms recorded at the PEDOT/Schiff electrode at a scan rate of 5  $\text{mV s}^{-1}$ . From this figure, it can be seen that the individual peak currents increased linearly with increasing concentrations of the individual metal ions in the binary solutions (Deshmukh et al. 2018).



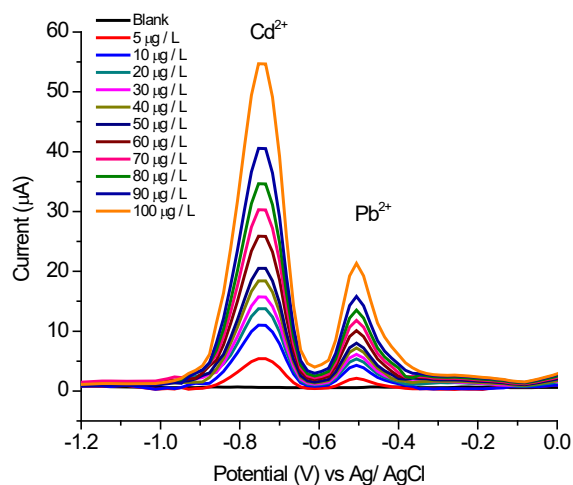

**Fig. 11** SWV response of poly(EDOT/Schiff) electrode for the simultaneous analysis of Cd(II) and Pb(II).

The findings of the study confirmed that the modified electrode shows the appropriate reliability and efficiency to be used for detecting Cd(II) and Pb(II) ions. Furthermore, the analytical performance of the PEDOT/Schiff electrode in this project was compared with previous work in the literature for Cd(II) and Pb(II) detection, as shown in **Table 4**.


**Table 4** Comparison of the analytical performance of the PEDOT/Schiff electrode with other modified electrodes.

Electrodes	Methods	Analytes	Detection limit	References
5-Br-PADAP	ASV	Pb (II)	0.1 $\mu\text{g L}^{-1}$	(Salmanipour and Taher 2011)
P1,2-DAAQ	SWASV	Cd (II) Pb (II)	0.3 $\mu\text{g} \cdot \text{L}^{-1}$ 0.58 $\mu\text{g} \cdot \text{L}^{-1}$	(Hassan et al. 2018)
GC/ p-1,8-DAN	SWV	Cd (II) Pb (II)	19 $\text{ng} \cdot \text{L}^{-1}$ 30 $\text{ng} \cdot \text{L}^{-1}$	(Hassan et al. 2019)
CNFs	ASV	Cd (II) Pb (II)	0.38 $\mu\text{g} \cdot \text{L}^{-1}$ 0.33 $\mu\text{g} \cdot \text{L}^{-1}$	(Qin et al. 2017)
polyamide 6/ Chitosan	SWV	Cd (II)	0.88 $\mu\text{g} \cdot \text{L}^{-1}$	(Migliorini et al. 2017)
PMTB	DPV	Cd (II) Pb (II)	0.35 $\mu\text{g L}^{-1}$ 0.18 $\mu\text{g L}^{-1}$	(Manikandan and Narayanan 2019)
polyaniline	SWASV	Cd (II) Pb (II)	4.43 $\mu\text{g L}^{-1}$ 3.30 $\mu\text{g L}^{-1}$	(Promphet et al. 2015)
poly(1,5-DAN)/MWCNTs	SWASV	Cd (II) Pb (II)	3.2 $\mu\text{g L}^{-1}$ 2.1 $\mu\text{g L}^{-1}$	(Vu et al. 2015)

## EDX measurements

In order to study the structure of polymer and show the presence of metal ions within the polymer surface, the elemental analysis of polymer electrode before and after adsorption of metal ions was accomplished via EDX analysis.


**Fig. 12A** illustrates the EDX spectra of the poly(EDTA/Schiff base) composite with C, N, O, and S as the major elements of the composite before adsorption of metal ions (Cd and Pb). After adsorption of metal ions (Cd and Pb), additional peaks attributable to Cd(II) and Pb(II) were observed in the EDX spectra (**Fig. 12(B)**), indicating binding between these ions and ligand groups on the polymer surface.

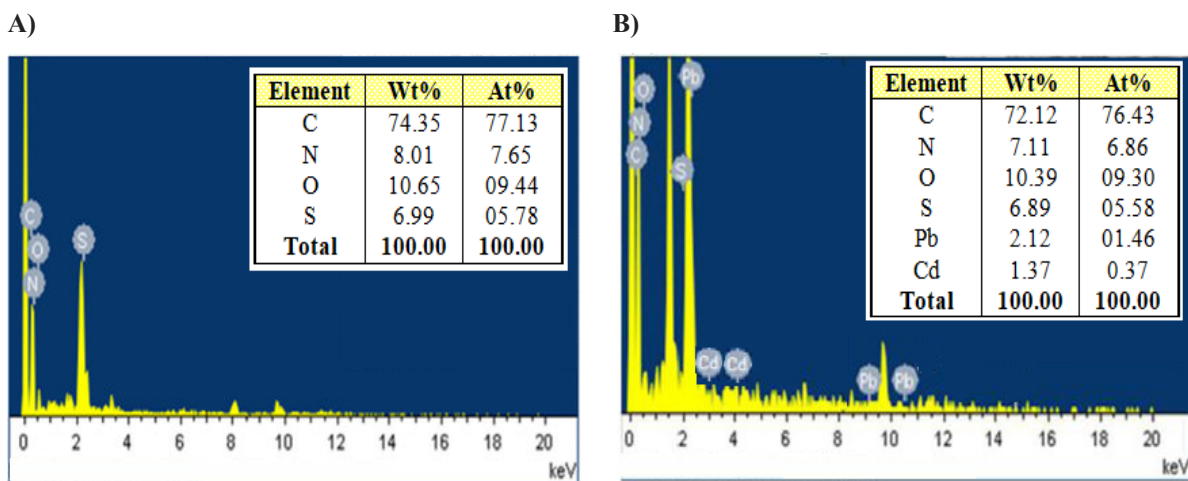

**Fig 12** EDX spectra showing elemental analysis of poly(EDTA/Schiff base) (A) before and (B) after adsorption of metal ions.

## Reactivation of PEDOT/Schiff electrode

Repeated usage of the modified electrode in the determination of the concentrations of metal ions necessitates the regeneration of the PEDOT/Schiff electrode. Reactivation of PEDOT/Schiff electrode was achieved by immersing in 0.1 M EDTA solution for 15 min and then washing with ultrapure water. A voltammogram recorded for PEDOT/Schiff electrode after reactivation was essentially congruous with the voltammogram of the PEDOT/Schiff electrode when reacted with metal ions, as shown in **Fig. 13** (red curve). This indicates that the incorporated metal ions had been totally removed from the PEDOT/Schiff electrode. Therefore, the reactivated PEDOT/Schiff electrode could be used for the detection of metal ions without any appreciable effect on the electro-activity.

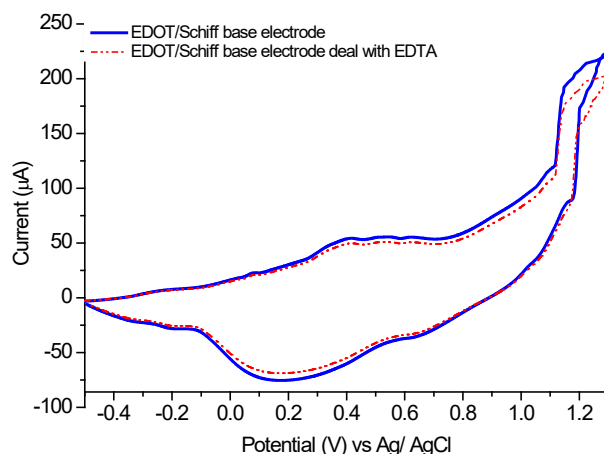

**Fig. 13** Cyclic voltammetric of PEDOT/Schiff modified electrode (blue curve) in  $\text{Bu}_4\text{NPF}_6$  aqueous electrolyte (red curve) after treating with 0.1 M EDTA

### Repeatability and reproducibility study

The repeatability of the PEDOT/Schiff electrode was determined under the optimised conditions using  $20 \mu\text{g L}^{-1}$  Cd(II) and Pb(II), respectively. Five consecutive measurements were taken using the same polymer electrode; the estimated relative standard deviations (RSD) were 3.4% and 2.8% for Cd(II) and Pb(II), respectively. Moreover, the reproducibility of the PEDOT/Schiff electrode was examined. This process required the preparation of five modified electrodes that were then used in the detection of  $20 \mu\text{g L}^{-1}$  Cd(II) and Pb(II), respectively. The RSD of the PEDOT/Schiff electrode was 3.8% and 3.1% for Cd(II) and Pb(II), respectively, which indicated that the PEDOT/Schiff electrode prepared has good repeatability and reproducibility.

### Interference study

To assess the selectivity of the modified electrode in the detection of metal ions, the effect of other ions on the response to Cd(II) and Pb(II) was investigated. In this study, various ions were chosen to act as interfering ions to investigate the selectivity of the PEDOT/Schiff electrode. Various ions ( $\text{Na}^+$ ,  $\text{K}^+$ ,  $\text{Ca}^{2+}$ ,  $\text{Mg}^{2+}$ ,  $\text{Ba}^{2+}$ ,  $\text{Cu}^{2+}$ ,  $\text{Hg}^{2+}$ ,  $\text{Al}^{3+}$ ,  $\text{Fe}^{3+}$ ,  $\text{NO}_3^-$ , and  $\text{Cl}^-$ ) were added to a solution containing  $20 \mu\text{g L}^{-1}$  Cd(II) and Pb(II). The addition of interfering ions did not lead to any perceptible difference in measurements, and these findings demonstrated that the electrochemical responses for Cd(II) and Pb(II) were not influenced by the interfering ions in any apparent way.

The interference experiments proved that additive ions have no perceptible interference effect to detection of target ions even when their concentrations exceed those of the ion of interest in the solution, at  $20 \mu\text{g L}^{-1}$  for Cd(II) and Pb(II), by 50-fold. However, 30-fold concentrations of  $\text{Fe}^{3+}$ ,  $\text{Cu}^{2+}$  and  $\text{Hg}^{2+}$  were found to have a slight influence on the determination of Cd(II) and Pb(II) concentrations. The intermetallic compounds that can form between metal ions

is a general problem in voltammetric methods, though this small change could be due to competition between iron and the target metal ions for active sites on the surface modified electrode. Further interference experiments of Cd(II) and Pb(II) with other earth-abundant toxic metals (e.g., Ni<sup>2+</sup> and Co<sup>2+</sup> ions) were carried out, the data for which are given in the supplementary information (**Table S1**).

**Table 5** Three interference analyses for various metal ions on the current responses of Cd(II) and Pb(II)

Interfering ions	Relative current change %	
	Cd (II)	Pb (II)
Na	0.19	0.25
K	0.36	0.42
Ca	-0.92	-0.85
Mg	1.17	1.09
Ba	1.67	1.35
Cu	6.34	5.92
Hg	-4.93	-5.62
Al	-0.56	-0.54
Fe	5.21	4.12
NO <sub>3</sub>	0.47	0.85
Cl	0.78	0.23

## Conclusions

The goal of this study was to modify functionalised polymer films for application in the electrochemical detection of metal ions in solution. The preparation of polymer films and overall operational performance was monitored using electrochemical (“iVt”) techniques. All modified electrodes were characterised using electrochemical (CV) and spectroscopic (FTIR) techniques. The findings indicated the successful formation of polymer films via cyclic voltammetry. Following the electropolymerisation, films were investigated using various scan rates (10 - 100 mV s<sup>-1</sup>) to examine electrochemical stability, demonstrating that redox peak currents are linearly dependent on scan rate. Further, the voltammetric data was used to estimate the surface coverage of the polymer films via Faraday’s law. A novel electrochemical tool for the quantification of metal ions, using an electroactive polymer, was developed. PEDOT functionalised with a Schiff base was electrodeposited on a Pt surface electrode by electrochemical techniques (CV) and then used for the detection of Cd(II) and Pb(II) ions in solution. The poly(EDOT/Schiff) electrode exhibited good sensitivity during electro-determination of trace amounts of metal ions (Cd(II) and Pb(II)), showing low limits of detection of 0.95 µg L<sup>-1</sup> for Cd(II) and 1.84 µg L<sup>-1</sup> for Pb(II). Cd(II) and Pb(II) ions were detected both individually and simultaneously using square wave voltammetry using the new poly(EDOT/Schiff) moieties.

## Acknowledgement

The authors would like to thank the Universities of Basrah, Koya and Kerbala for providing the required materials and instruments for this work.

### Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that might have influenced the work reported in this paper.

### References

- Abd Ali LI, Ismail HK, Aboul-Enein HY (2021) A nanocomposite based on polyaniline, nickel and manganese oxides for dye removal from aqueous solutions. *Int J Environ Sci Technol* 18:2031–2050. <https://doi.org/10.1007/s13762-020-02961-0>
- Alesary HF, Ismail HK, Khudhair AF, Mohammed MQ (2018) Effects of dopant ions on the properties of polyaniline conducting polymer. *Orient J Chem* 34:2525-2533. <https://doi.org/10.13005/ojc/340539>
- Alesary HF, Ismail HK, Mohammed MQ, Mohammed HN, Abbas ZK, Barton S (2021) A comparative study of the effect of organic dopant ions on the electrochemical and chemical synthesis of the conducting polymers polyaniline, poly(o-toluidine) and poly(o-methoxyaniline). *Chem Pap* 75: 5087-5101. <https://doi.org/10.1007/s11696-020-01477-8>
- Almashal FA, Mohammed MQ, Hassan QMA, Emshary CA, Sultan HA, Dhumad AM (2020) Spectroscopic and thermal nonlinearity study of a Schiff base compound. *Opt Mater (Amst)* 100:109703. <https://doi.org/10.1016/j.optmat.2020.109703>
- Barsan MM, Ghica ME, Brett CMA (2015) Electrochemical sensors and biosensors based on redox polymer/carbon nanotube modified electrodes: a review. *Anal Chim Acta* 881:1–23. <https://doi.org/10.1016/j.aca.2015.02.059>
- Bidan G (1992) Electroconducting conjugated polymers: new sensitive matrices to build up chemical or electrochemical sensors. A review. *Sensors Actuators B Chem* 6:45–56. [https://doi.org/10.1016/0925-4005\(92\)80029-W](https://doi.org/10.1016/0925-4005(92)80029-W)
- Bobacka J (2006) Conducting polymer-based solid-state ion-selective electrodes. *Electroanal An Int J Devoted to Fundam Pract Asp Electroanal* 18:7–18. <https://doi.org/10.1002/elan.200503384>
- Bozzini B, Bocchetta P, Alemán B, Amati M, Gianoncelli A, Gregoratti L, Sezen H, Taurino A, Kiskinova M (2015) Electrodeposition and pyrolysis of Mn/polypyrrole nanocomposites: a study based on soft X ray absorption, fluorescence and photoelectron microspectroscopies. *J Mater Chem A* 3: 19155-19167. <https://doi.org/10.1039/C5TA05572E>
- Brown RM, Hillman AR (2012) Electrochromic enhancement of latent fingerprints by poly (3, 4-ethylenedioxythiophene). *Phys Chem Chem Phys* 14:8653–8661. <https://doi.org/10.1039/C2CP40733G>
- Dang VH, Yen PTH, Giao NQ, et al (2018) A versatile carbon fiber cloth-supported Au nanodendrite sensor for simultaneous determination of Cu(II), Pb(II) and Hg(II). *Electroanalysis* 30:2222–2227. <https://doi.org/10.1002/elan.201800332>
- Darmanin T, Guittard F (2013) Superoleophobic surfaces with short fluorinated chains. *Soft Matter* 9:5982–5990. <https://doi.org/10.1039/C3SM50643F>

- Deshmukh MA, Celiesiute R, Ramanaviciene A, Shirsat MD, Ramanavicius A (2018) EDTA\_PANI/SWCNTs nanocomposite modified electrode for electrochemical determination of copper (II), lead (II) and mercury (II) ions. *Electrochim Acta* 259:930-938. <https://doi.org/10.1016/j.electacta.2017.10.131>
- Duan C, Liu Z, Yuan L, Zhu H, Luo H, Yan K (2020) PEDOT:PSS-metal oxide composite electrode with regulated wettability and work function for high-performance inverted perovskite solar cells. *Adv Optical Mater* 8: 2000216. <https://doi.org/10.1002/adom.202000216>
- Etoroki AM, Hillman AR, Ryder KS, Glidle A (2007) Quartz crystal microbalance determination of trace metal ions in solution. *J Electroanal Chem* 599:275–287. <https://doi.org/10.1016/j.jelechem.2006.03.020>
- Fourou H, Zazoua A, Braiek M, Jaffrezic-Renault N (2016) An enzyme biosensor based on beta-galactosidase inhibition for electrochemical detection of cadmium (II) and chromium (VI). *Int J Environ Anal Chem* 96:872–885. <https://doi.org/10.1080/03067319.2016.1209659>
- Guadalupe AR, Abruna HD (1985) Electroanalysis with chemically modified electrodes. *Anal Chem* 57:142–149. <https://doi.org/10.1021/ac00279a036>
- Gumpu MB, Sethuraman S, Krishnan UM, Rayappan JBB (2015) A review on detection of heavy metal ions in water—an electrochemical approach. *Sensors Actuators B Chem* 213:515–533. <https://doi.org/10.1016/j.snb.2015.02.122>
- Han J, Yu J, Guo Y, Wang L, Song Y (2020) COF<sub>BTLp-1</sub>/three-dimensional macroporous carbon electrode for simultaneous electrochemical detection of Cd<sup>2+</sup>, Pb<sup>2+</sup>, Cu<sup>2+</sup> and Hg<sup>2+</sup>. *Sensors Actuators B Chem* 321:128498. <https://doi.org/10.1016/j.snb.2020.128498>
- Hassan KM, Elhaddad GM, AbdelAzzem M (2019) Voltammetric determination of cadmium (II), lead (II) and copper (II) with a glassy carbon electrode modified with silver nanoparticles deposited on poly (1, 8-diaminonaphthalene). *Microchim Acta* 186:440. <https://doi.org/10.1007/s00604-019-3552-0>
- Hassan KM, Gaber SE, Altahan MF, Azzem MA (2018) Novel sensor based on poly (1, 2-diaminoanthraquinone) for individual and simultaneous anodic stripping voltammetry of Cd<sup>2+</sup>, Pb<sup>2+</sup>, Cu<sup>2+</sup> and Hg<sup>2+</sup>. *Electroanalysis* 30:1155–1162. <https://doi.org/10.1002/elan.201800097>
- He B, Shen XF, Nie J, et al (2018) Electrochemical sensor using graphene/Fe<sub>3</sub>O<sub>4</sub> nanosheets functionalized with garlic extract for the detection of lead ion. *J Solid State Electrochem* 22:3515–3525. <https://doi.org/10.1007/s10008-018-4041-9>
- Hillman AR, Ryder KS, Ismail HK, Unala A, Voorhaara A (2017) Fundamental aspects of electrochemically controlled wetting of nanoscale composite materials. *Faraday Discuss* 199:75–99. <https://doi.org/10.1039/C7FD00060J>
- Huang H, Zhu W, Gao X, Liu X, Ma H (2016) Synthesis of a novel electrode material containing phytic acid-polyaniline nanofibers for simultaneous determination of cadmium and lead ions. *Anal Chim Acta* 947:32–41. <https://doi.org/10.1016/j.aca.2016.10.012>
- Intarakamhang S, Schuhmann W, Schulte A (2013) Robotic heavy metal anodic stripping voltammetry: ease and efficacy for trace lead and cadmium electroanalysis. *J Solid State Electrochem* 17:1535–1542. <https://doi.org/10.1007/s10008-013-2018-2>

- Ismail HK, Alesary HF, Al-Murshedi AY, Kareem JH (2019a) Ion and solvent transfer of polyaniline films electrodeposited from deep eutectic solvents via EQCM. *J Solid State Electrochem* 23:3107–3121. <https://doi.org/10.1007/s10008-019-04415-1>
- Ismail HK, Alesary HF, Mohammed MQ (2019b) Synthesis and characterisation of polyaniline and/or MoO<sub>2</sub>/graphite composites from deep eutectic solvents via chemical polymerization. *J Polym Res* 26:65. <https://doi.org/10.1007/s10965-019-1732-6>
- Lattach Y, Fourati N, Zerrouki C, Fougion JM, Garnier F, Pernelle C, Remit S (2012) Molecularly imprinted surface acoustic wave sensors: The synergy of electrochemical and gravimetric transductions in chemical recognition processes. *Electrochim Acta* 73:36–44. <https://doi.org/10.1016/j.electacta.2011.11.119>
- Lei W, Si W, Xu Y, Gu Z, Hao Q (2014) Conducting polymer composites with graphene for use in chemical sensors and biosensors. *Microchim acta* 181:707–722. <https://doi.org/10.1007/s00604-014-1160-6>
- Li Y, Ran G, Lu G, Ni X, Liu D, Sun J, Xie C, Yao D, Bai W (2019) Highly sensitive label-free electrochemical aptasensor based on screen-printed electrode for detection of cadmium (II) ions. *J Electrochem Soc* 166:B449. <https://doi.org/10.1149/2.0991906jes>
- Lu Y, Liang X, Niyungeko C, Zhou J, Xu J, Tian G (2018) A review of the identification and detection of heavy metal ions in the environment by voltammetry. *Talanta* 178:324–338. <https://doi.org/10.1016/j.talanta.2017.08.033>
- Manikandan R, Narayanan SS (2019) Simultaneous anodic stripping voltammetric determination of Pb(II) and Cd(II) using poly methyl thymol blue film–modified electrode. *Ionics* 25:6083–6092. <https://doi.org/10.1007/s11581-019-03143-w>
- Michalska A, Gałuszkiewicz A, Ogonowska M, Ocypa M, Maksymiuk K (2004) PEDOT films: multifunctional membranes for electrochemical ion sensing. *J Solid State Electrochem* 8:381–389. <https://doi.org/10.1007/s10008-003-0459-8>
- Migliorini FL, Sanfelice RC, Pavinatto A, Steffens J, Steffens C, Correa DS (2017) Voltammetric cadmium(II) sensor based on a fluorine doped tin oxide electrode modified with polyamide 6/chitosan electrospun nanofibers and gold nanoparticles. *Microchim Acta* 184:1077–1084. <https://doi.org/10.1007/s00604-017-2082-x>
- Mohammed MQ (2018) Patterned functionalisation of conducting polymer films. Thesis, University of Leicester. <https://hdl.handle.net/2381/42227>
- Mohammed MQ, Jassem AM, Al-Shawi JMS, Alesary HF (2020) Comparative electrochemical behavior of poly (3-aminobenzoic acid) films in conventional and non-conventional solvents. In: AIP Conference Proceedings. AIP Publishing LLC 2290: 030029. <https://doi.org/10.1063/5.0027520>
- Morante-Zarcero S, Pérez-Quintanilla D, Sierra I (2015) A disposable electrochemical sensor based on bifunctional periodic mesoporous organosilica for the determination of lead in drinking waters. *J Solid State Electrochem* 19:2117–2127. <https://doi.org/10.1007/s10008-015-2889-5>
- Muralikrishna S, Nagaraju DH, Balakrishna RG, Surendra W, Ramakrishnappa T, Shivanandareddy AB (2017) Hydrogels of polyaniline with graphene oxide for highly sensitive electrochemical determination of lead ions. *Anal Chim Acta* 990:67–77. <https://doi.org/10.1016/j.aca.2017.09.008>
- Niu L, Kvarnström C, Fröberg K, Ivaska A (2001) Electrochemically controlled surface morphology and crystallinity

- in poly (3, 4-ethylenedioxythiophene) films. *Synth Met* 122:425–429. [https://doi.org/10.1016/S0379-6779\(00\)00562-2](https://doi.org/10.1016/S0379-6779(00)00562-2)
- Ouyang L, Wei B, Kuo CC, Pathak S, Farrell B, Martin DC (2017) Enhanced PEDOT adhesion on solid substrates with electrografted P (EDOT-NH<sub>2</sub>). *Sci Adv* 3:e1600448. <https://doi.org/10.1126/sciadv.1600448>
- Oztekin Y, Ramanaviciene A, Ryskevicius N, Yazicigil Z, Üstündağ Z, Solak AO and Ramanavicius A (2011) 1,10-Phenanthroline modified glassy carbon electrode for voltammetric determination of cadmium(II) ions. *Sens. Actuators B Chem* 157: 146-153. <https://doi.org/10.1016/j.snb.2011.03.041>
- Pandey SK, Sachan S, Singh SK (2019) Ultra-trace sensing of cadmium and lead by square wave anodic stripping voltammetry using ionic liquid modified graphene oxide. *Mater Sci Energy Technol* 2:667–675. <https://doi.org/10.1016/j.msct.2019.09.004>
- Pillalamarri SK, Blum FB, Tokuhiko AT, Bertino MF (2005) One-pot synthesis of polyaniline-metal nanocomposites. *Chem Mater* 17: 5941-5944. <https://doi.org/10.1021/cm050827y>
- Promphet N, Rattanarat P, Rangkupan R, Chailapakul O, Rodthongkum N (2015) An electrochemical sensor based on graphene/polyaniline/polystyrene nanoporous fibers modified electrode for simultaneous determination of lead and cadmium. *Sensors Actuators B Chem* 207:526–534. <https://doi.org/10.1016/j.snb.2014.10.126>
- Qin D, Gao S, Wang L, et al (2017) Three-dimensional carbon nanofiber derived from bacterial cellulose for use in a Nafion matrix on a glassy carbon electrode for simultaneous voltammetric determination of trace levels of Cd(II) and Pb(II). *Microchim Acta* 184:2759–2766. <https://doi.org/10.1007/s00604-017-2260-x>
- Raghu GK, Sampath S, Pandurangappa M (2012) Chemically functionalized glassy carbon spheres: a new covalent bulk modified composite electrode for the simultaneous determination of lead and cadmium. *J Solid State Electrochem* 16:1953–1963. <https://doi.org/10.1007/s10008-011-1595-1>
- Rahman MD, Kumar P, Park DS, Shim YB (2008) Electrochemical sensors based on organic conjugated polymers. *Sensors* 8:118–141. <https://doi.org/10.3390/s8010118>
- Salmanipour A, Taher MA (2011) An electrochemical sensor for stripping analysis of Pb(II) based on multiwalled carbon nanotube functionalized with 5-Br-PADAP. *J Solid State Electrochem* 15:2695–2702. <https://doi.org/10.1007/s10008-010-1197-3>
- Sapstead RM, Corden N, Hillman AR (2015) Latent fingerprint enhancement via conducting electrochromic copolymer films of pyrrole and 3, 4-ethylenedioxythiophene on stainless steel. *Electrochim Acta* 162:119–128. <https://doi.org/10.1016/j.electacta.2014.11.061>
- Schultheiss A, Carella A, Pouget S, et al (2020) Water content control during solution-based polymerization: a key to reach extremely high conductivity in PEDOT thin films. *J Mater Chem C* 8:17254–17260. <https://doi.org/10.1039/D0TC04899B>
- Shervedani RK, Akrami Z (2013) Gold–deferrioxamine nanometric interface for selective recognition of Fe (III) using square wave voltammetry and electrochemical impedance spectroscopy methods. *Biosens Bioelectron* 39:31–36. <https://doi.org/10.1016/j.bios.2012.06.025>
- Sun Y, Du H, Deng Y, Lan Y, Feng C (2016) Preparation of polyacrylamide via surface-initiated electrochemical-mediated atom transfer radical polymerization (SI-eATRP) for Pb<sup>2+</sup> sensing. *J Solid State Electrochem* 20:105–



113. <https://doi.org/10.1007/s10008-015-3008-3>

- Vilas-Boas M, Freire C, De Castro B, Hillman AR (1998) Electrochemical characterization of a novel salen-type modified electrode. *J Phys Chem B* 102:8533–8540. <https://doi.org/10.1021/jp982160r>
- Vu HD, Nguyen LH, Nguyen TD, Nguyen HB, Nguyen TL, Tran DL (2015) Anodic stripping voltammetric determination of Cd<sup>2+</sup> and Pb<sup>2+</sup> using interpenetrated MWCNT/P1, 5-DAN as an enhanced sensing interface. *Ionics* 21:571–578. <https://doi.org/10.1007/s11581-014-1199-8>
- Wang J, Bian C, Tong J, Sun J, Xia S (2012) Simultaneous detection of copper, lead and zinc on tin film/gold nanoparticles/gold microelectrode by square wave stripping voltammetry. *Electroanalysis* 24:1783–1790. <https://doi.org/10.1002/elan.201200131>
- Xu Z, Fan X, Ma Q, et al (2019) A sensitive electrochemical sensor for simultaneous voltammetric sensing of cadmium and lead based on Fe<sub>3</sub>O<sub>4</sub>/multiwalled carbon nanotube/laser scribed graphene composites functionalized with chitosan modified electrode. *Mater Chem Phys* 238:121877. <https://doi.org/10.1016/j.matchemphys.2019.121877>
- Yao Y, Wu H, Ping J (2019) Simultaneous determination of Cd(II) and Pb(II) ions in honey and milk samples using a single-walled carbon nanohorns modified screen-printed electrochemical sensor. *Food Chem* 274:8–15. <https://doi.org/10.1016/j.foodchem.2018.08.110>
- Yin T, Pan D, Qin W (2012) A solid-contact Pb<sup>2+</sup>-selective polymeric membrane electrode with Nafion-doped poly (pyrrole) as ion-to-electron transducer. *J Solid State Electrochem* 16:499-504. <https://doi.org/10.1007/s10008-011-1358-z>
- Zhai Z, Huang N, Zhuang H, et al (2018) A diamond/graphite nanoplatelets electrode for anodic stripping voltammetric trace determination of Zn(II), Cd(II), Pb(II) and Cu(II). *Appl Surf Sci* 457:1192–1201. <https://doi.org/10.1016/j.apsusc.2018.06.266>
- Zhang Y, Li C, Su Y, Mu W, Han X (2020) Simultaneous detection of trace Cd(II) and Pb(II) by differential pulse anodic stripping voltammetry using a bismuth oxycarbide/nafion electrode. *Inorg Chem Commun* 111:107672. <https://doi.org/10.1016/j.inoche.2019.107672>